

---

---

# THE OLD POTTER'S ALMANACK

---

---

Volume Twenty-three, Number One: October 2018. ISSN 0965-7479

---

## EDITORIAL

Dear Reader,

This October issue of *The Old Potter's Almanack* presents two stimulating papers. The first, by Ester Lunardon, unveils the chaîne opératoire of the Iron Age potters at the northern Italian site of Castion Di Erbè. The second, by Cristian Eduard Ștefan, focuses on the rare evidence of ceramic bases with vegetal impressions at Neolithic archaeological sites.

Lunardon applies a systematic approach, using traditional and scientific techniques (macro-observation and X-ray radiography), to examine the forming techniques of a variety of Iron Age ceramic shapes, always considering the morphology and possible vessel function. The author discusses in detail the importance of using the two methods, and in particular how X-ray radiography can detect precisely the coils and joints, and help in identifying the primary forming techniques of the pots, in contrast with secondary forming techniques. Finally, she also illustrates how to identify the paddle-and-anvil technique, and its 'technical continuity' with metallurgical production.


The second paper presents macroscopic analyses of the vegetal impressed patterns on vessel bases from the Romanian site of Șoimuș-La Avicola (Ferma 2). To try to identify the plant species used to make the mat on which the pots were probably dried, the author undertook an experiment using local club-rush. Although the patterns obtained through this experiment do not match the Neolithic weaving patterns, the author widens the case-study, noting that similar weaving patterns were detected at other sites of the 6<sup>th</sup> and 5<sup>th</sup> millennia BC. Some of these patterns are surprisingly complex. This indirect evidence of weaving is particularly significant in the Balkans; although Neolithic spindle-whorls are recurrent finds, organic material (including textiles) is almost entirely absent.

I hope you will enjoy this issue.


*Michela Spataro*

## IN THIS ISSUE

*The pottery technology of the Iron Age site of Castion Di Erbè (Verona, north-eastern Italy)* **Page 2**  
Ester Lunardon

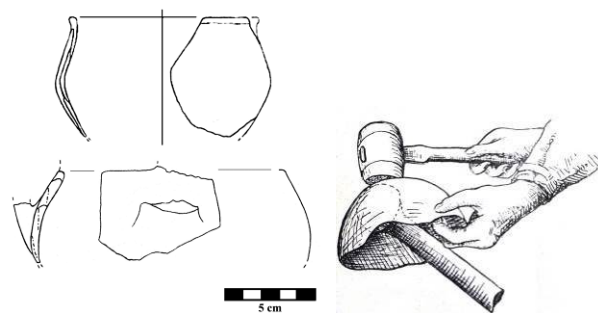

*Impressed vessel bottoms from Șoimuș-La Avicola (Ferma 2), Hunedoara county, Romania* **Page 15**  
Cristian Eduard Ștefan

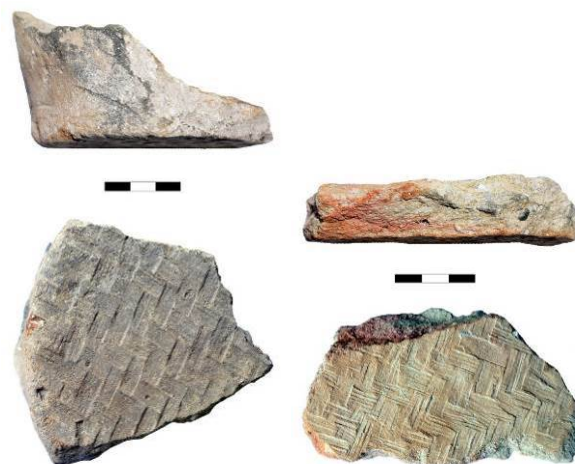

*Conference Diary*

**Page 26**

## THE POTTERY TECHNOLOGY OF THE IRON AGE SITE OF CASTION DI ERBÈ (VERONA, NORTH-EASTERN ITALY)

Ester Lunardon

*Independent Researcher*

Email: [ester\\_luna@hotmail.it](mailto:ester_luna@hotmail.it)

### Introduction

Excavations carried out between 1972 and 1976 in the Iron Age site of Castion di Erbè (Verona, north-eastern Italy)<sup>1</sup> provided a large quantity of ceramic materials available for study. This article presents the results of a Master's Dissertation, recently conducted at the University of Padua under the guidance of Massimo Vidale and Giovanni Leonardi, the aim of which was to understand how pottery was produced throughout the two centuries-long occupation of the site, with special focus on the forming techniques.

Castion di Erbè is situated in the Po plain, next to Verona (north-eastern Italy – Figure 1), and dated between the 8<sup>th</sup> and the first decades of the 6<sup>th</sup> century BC. The Iron Age village, *ca.* 4 hectares in area, was settled in a strategic position on the bank of the river Tartaro and was enclosed by a ditch<sup>2</sup>.

The site was badly damaged by agricultural works, so that the only preserved features at the time of the rescue excavation were pits filled by secondary deposits<sup>3</sup>. Because of the very disturbed stratigraphical context, the chronology of the site is essentially based on the typo-chronological analysis of the pottery. However, materials recovered in the pits have been a very interesting source of information, showing that many different craft activities used to take place at the site<sup>4</sup>, highlighting the strong cultural link that must have connected Castion di Erbè with the other Iron Age sites of

Padua and Este, central places of the polity of the ancient Veneto region.

### The study of the forming techniques

Out of all the ceramic material recovered on site, 127 sherds were selected for study. The reasons guiding the selection were the following:

1. typo-chronological information: sherds were chosen, which had previously been drawn and studied from a typo-chronological point of view, so that a chronology of the pottery was available<sup>5</sup>;
2. technological interest: larger sherds and fragments showing particular diagnostic features were preferred;
3. morphological and chronological issues: sherds were selected from a limited range of shapes<sup>6</sup> (*tazzette* or bowls, *coppe* or truncated cone-like restricted bowls, *scodelloni* or large bowls/basins, *olle* or slightly restricted small to medium jars, *situliformi* or inverted-truncated cone-like restricted vessels, similar in shape to bronze buckets, and *dolii* or large coarse ware jars), making sure to take into account sherds dating to the entire occupation period of the site (Figure 2). In accordance to this, materials with imprecise chronology were excluded.

The sherds were analysed in two phases and with two different methods:

1. Direct observation with the naked eye of surfaces and fractures. In this phase the guiding criteria for identifying the forming techniques were based on a summary of the existing literature with special reference to a work by Sara Levi which can be used as good background for the study of the pottery technology in Italy (Levi 2010; Tite 2008; Cuomo di Caprio 2007; Vidale 1992; 2007; Rice 1987; Rye 1981; Vandiver and Wheeler 1991). The critical examination of this archaeological literature resulted in the definition of some diagnostic characteristics of the four main forming techniques, which are summarised in Table 1<sup>7</sup>.

<sup>1</sup> Works were led by Giovanni Leonardi and funded by the local Soprintendenza (Leonardi 1975 a and b; 1976; 1977; 1979; 2002; Capuis *et al.* 1990).

<sup>2</sup> The excavation of the enclosure system revealed the presence of at least two phases of occupation: a first ditch was backfilled and replaced by another larger one, probably as a result of the expansion of the site. Archaeological investigations also suggest that both ditches should not have been used for drainage purposes, but more probably had a defensive function.

<sup>3</sup> Some post-holes could be identified too, which could have represented a wooden and plaster hut. Bettinardi and Leonardi 2002, 287-302.

<sup>4</sup> Pottery making is indicated by the presence of three very worn polishing stone tools (*brunitai*) and of some half-processed grog (Favero 1994-5).

<sup>5</sup> In the last 20 years two Master's dissertations and a PhD study analysed the typochronology of the pottery of Castion di Erbè (see Toscani 1995-6, Bettinardi 1996-7 and Rossi 2008). The PhD dissertation by Rossi represents the most complete effort to summarise the typochronology of the pottery of the site and was therefore given special attention.

<sup>6</sup> The morphological grouping accords with the above mentioned typo-chronological studies. The seven selected morphological groups do not represent the whole range of shapes identified at the site, but are just the most common ones.

<sup>7</sup> The paddle-and-anvil technique is here considered as a secondary forming technique, and therefore not listed in Table 1. The parameters used in the table (joints, orientation of the fractures, edges, etc.) will mainly depend on the primary forming technique (mostly coiling) associated to the paddle-and-anvil technique. The only parameter which the paddle-and-anvil technique actually seems to have an impact on is the walls thickness. However, this assertion is not based on a summary of existing literature, as all the other information in the table, but on the results of this work, which will be discussed below.

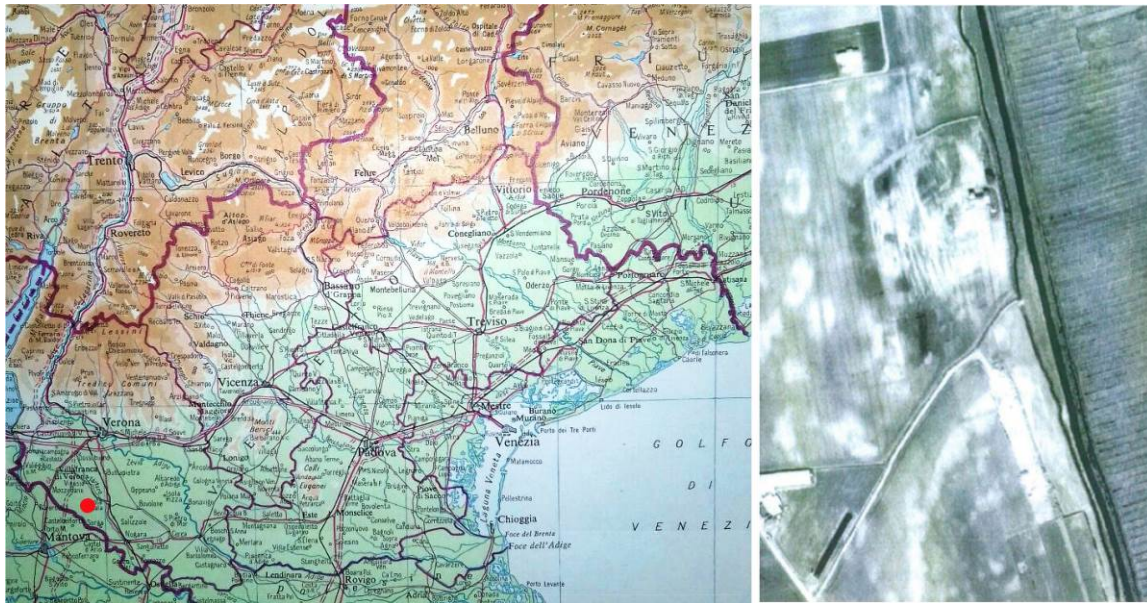


Figure 1. Map showing the location of Castion di Erbè, next to Verona, north-eastern Italy (modified from Atlas Zanichelli 1999). Aerial photo of the site (1985). The trapezoidal enclosure ditch of the settlement is clearly visible (from Bettinardi 1996-7, tav. 3b).

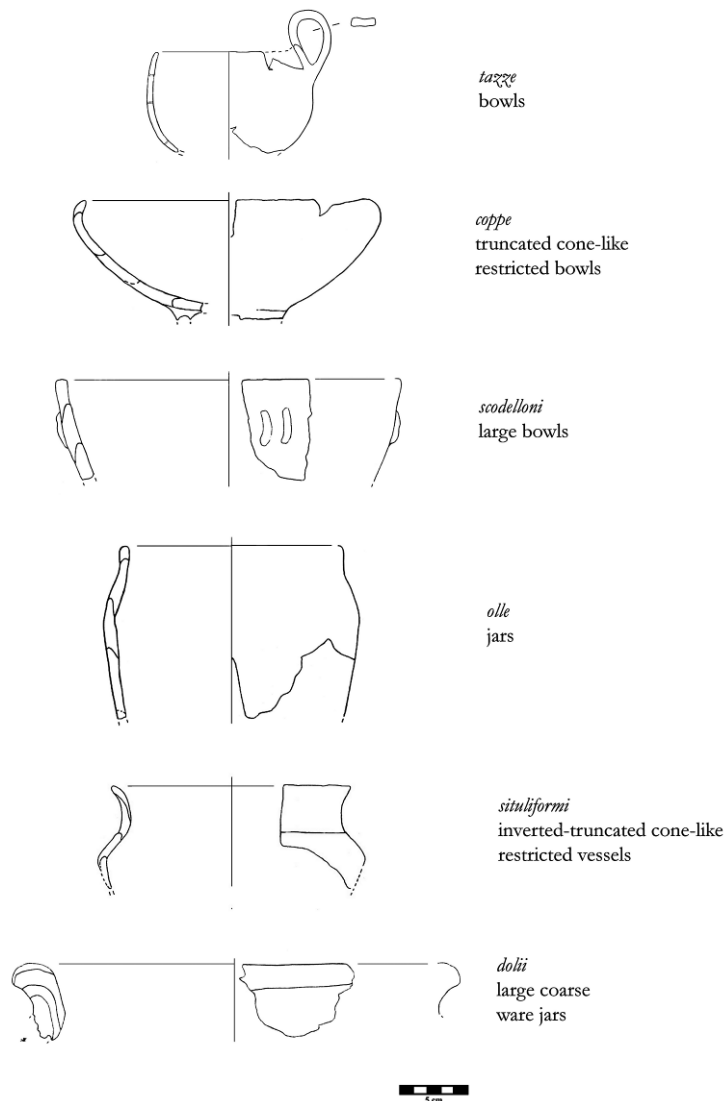


Figure 2. Illustration of the morphological types considered in this study. A drawing for each shape has been selected as an example.



	SLAB BUILDING	MOULDING	COILING	WHEEL-THROWING
Joints visible in sections	Yes	No (or just in the case of added parts)	No	No (or just in the case of added parts)
Orientation of the fractures	Oblique fractures	Oblique fractures	Horizontal fractures	Oblique fractures
Edges	Curved	Curved	Straight	Characteristic "petal"-shaped edges
Thickness of the walls	Great variability	Remarkable variability sometimes with delimited hollows	Slight variations along horizontal patterns. Generally constant thickness	Slight periodic variations. Thickness tends to reduce from the foot to the rim.
Surface traces	Cracks near the joints		Cracks near the joints	Spiral-oriented traces on the inside
Position of the fractures	At the joints		Horizontally along the vessel, at the joints	
Shape		Rigid straight profile		Curvy and continuous profile
Symmetry	Sometimes oval-shaped vessels and <b>asymmetry</b>	Depending on the mould	Sometimes oval-shaped vessels and <b>asymmetry</b>	Sometimes oval-shaped vessels but <b>symmetry</b>

Table 1. Summary of the diagnostic characteristics of the four main forming techniques as observable with the naked eye.

By observing each sherd with this method, some first-stage hypotheses about the forming techniques were formulated, which were recorded through a written description and a technological drawing of each sherd<sup>8</sup> (Figure 3).

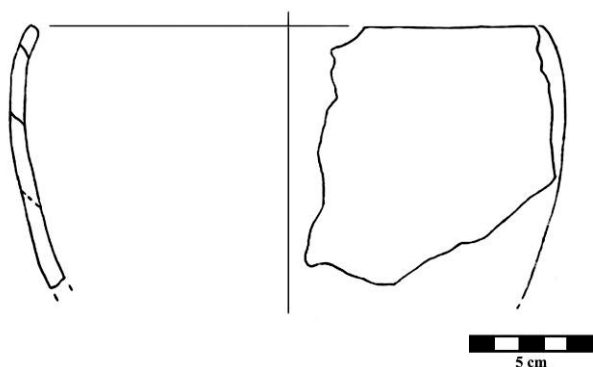


Figure 3. Example of a drawing of a bowl. In the section the joints between coils are shown: clearer joints are indicated through continuous lines, whereas dashed lines have been used when joints were identified with a lower degree of confidence.

2. In a second stage of the research, X-radiography was used as a method of validation to test the

hypotheses previously formulated<sup>9</sup>, even if it must be stressed that the number of X-radiographed sherds (23 out of 127)<sup>10</sup> cannot be considered statistically significant. The selection of the sherds was based on the following principles:

- the dimension of the sherds: larger sherds were mainly preferred;
- the number of fragments for each vessel;
- specific technological questions arising from the direct observation of the materials.

The disposition of the inclusions and the disposition and the shape of the voids in the ceramic fabric were considered diagnostic elements for the interpretation of the radiographic images (Table 2)<sup>11</sup>. The combination of these two approaches – visual observation and X-radiography – resulted in the

<sup>8</sup> The typological drawings of the sherds, made by Rossi (2008) and Toscani (1995-6), were used as a base, to which the technological information such as the position of the coils in the fractures, wear marks, etc. were added.

<sup>9</sup> The analyses were done at the Radiology Department of the Hospital of Cittadella (Padua); the instrument used was a Philips Digital Diagnost with CR system. The results were processed by the open source software ImageJ (National Institute of Health, USA).

<sup>10</sup> Four bowls, five cone-like truncated bowls, five basins, four jars, four *situliformi* and one large coarse-ware jar were selected for X-ray analysis.

<sup>11</sup> The identification of the diagnostic features for the radiographic analysis was especially based on Berg 2008, 2009, 2011a and 2011b; Levi 2010, Carr 1990 and 1993; Carr and Komorowski 1995; Carr and Riddick 1990; Cazzella *et al.* 1994; Courty and Roux 1995; Ellingson *et al.* 1998; Lang and Middleton 2005; Rye 1977; Mannoni and Giannichedda 1996; Vandiver and Tumosa 1995; Vandiver *et al.* 1991.

identification of the forming techniques, as shown in Figure 4.

It must be noted that the number of different techniques varies in relation to the morphology of the vessels. The large bowls or basins, for example, which would presumably have had a practical function in relation to cooking, were almost

exclusively made by coiling, whereas more refined vessels such as bowls were made applying a greater variety of techniques. This is possibly due to the fact that the representative function of the bowls required a greater technological complexity that in the case of the basins was not considered useful. Observation showed that coiling was the most frequently used and the most versatile forming technique, as it was

	Inclusions	Voids
Coiling	Horizontal alignments clustered along the centre of the coils	Horizontal alignments; voids have horizontally elongated and rounded shape
Moulding and slab-building	Random disposition	Random disposition; voids have elongated and rounded shape
Wheel-throwing	Oblique alignments; inclusions aren't usually larger than ¼ of the wall thickness	Little porosity. Oblique alignments; voids have very elongated shape

Table 2. Summary of the diagnostic elements on which the interpretation of the radiographic analysis was based.

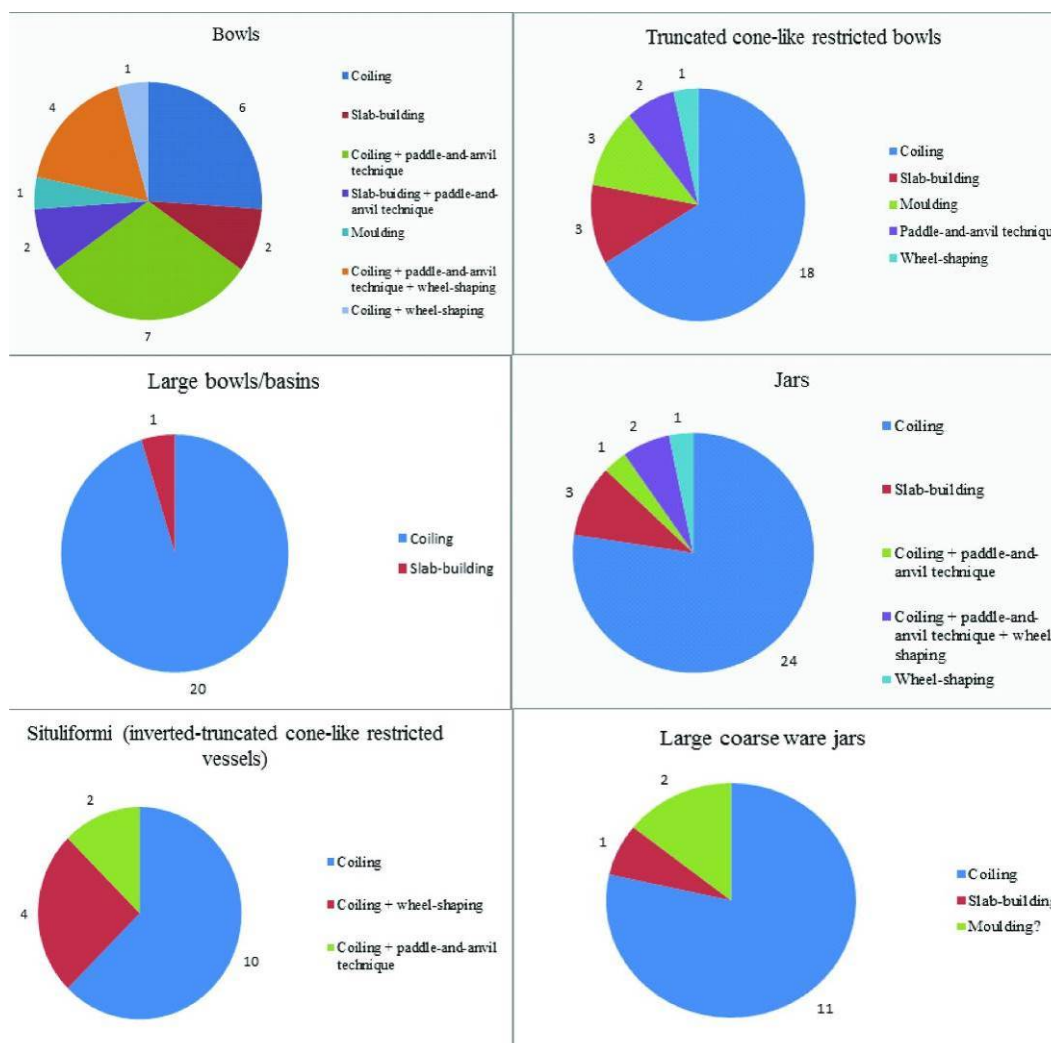


Figure 4. Excel pie charts indicating the percentage presence of the different forming techniques in the different morphological groups. It must be noted that the number of different techniques varies in relation to the morphology of the vessels. The large bowls or basins, for example, which would presumably have had a practical function in relation to cooking, were almost exclusively made by coiling, whereas more refined vessels such as bowls were made applying a greater variety of techniques. This is possibly due to the fact that the representative function of the bowls required a greater technological complexity that in the case of the basins was not considered useful.

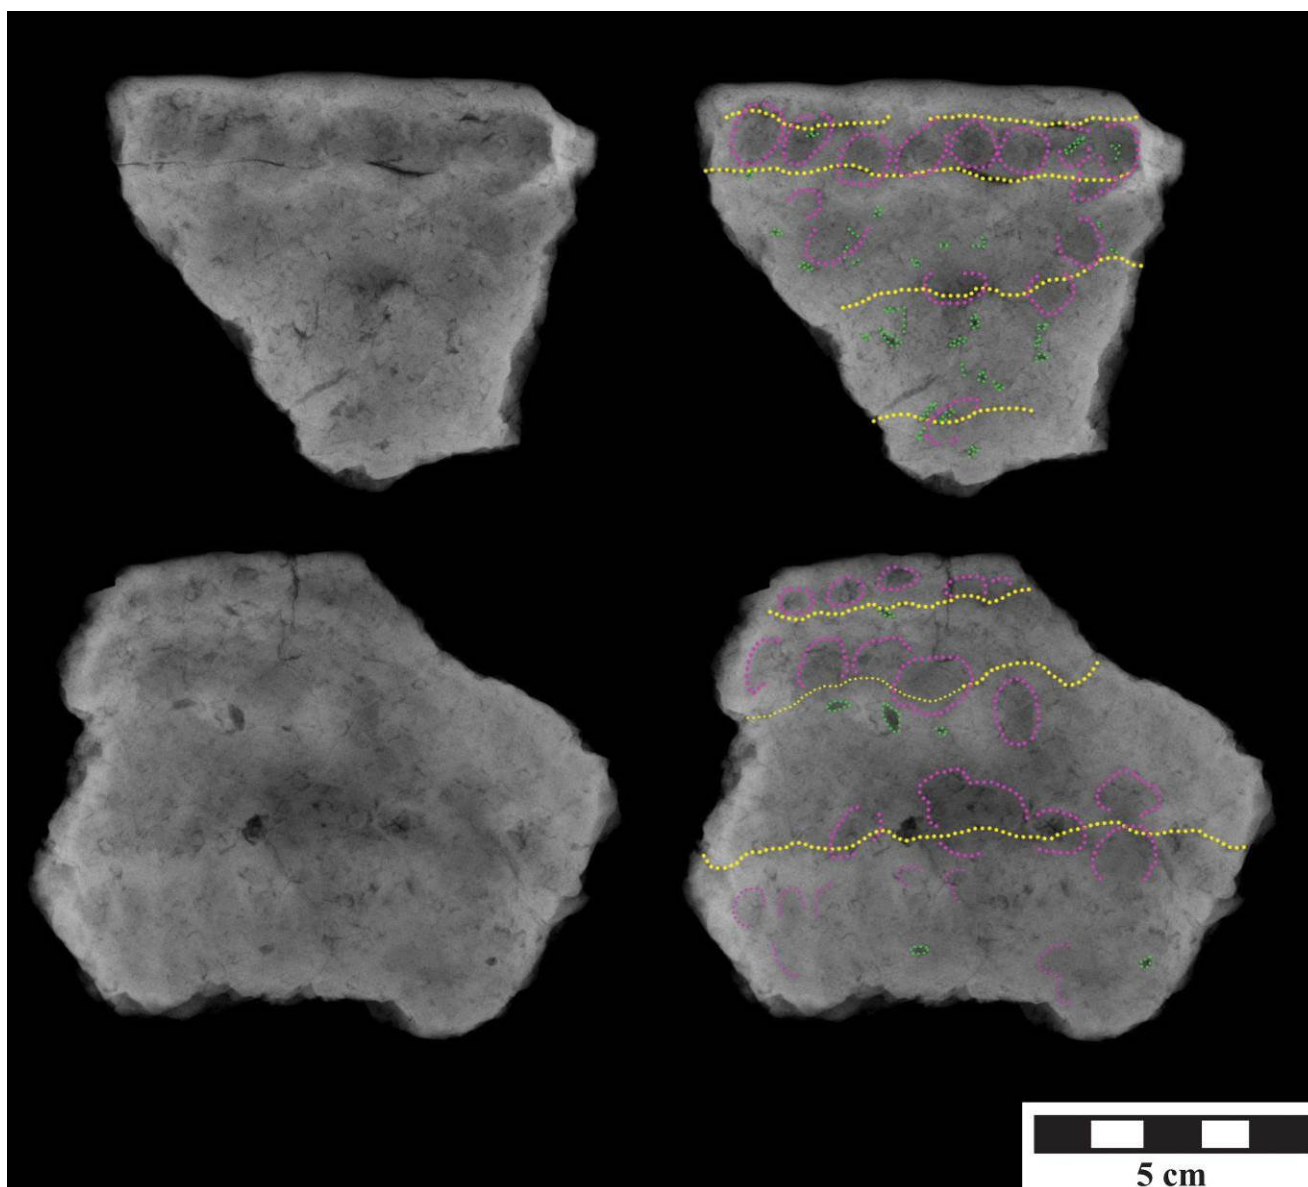


Figure 5. Examples of X-radiographic images of two coarse ware basins made by coiling, showing the specific “motor habit” of serial finger prints (highlighted in pink) approximately aligning with coil-joins (highlighted in yellow).

applied in every different morphological group. X-radiography showed in more detail a particular practice involved in this forming process. In all the X-rayed basins, as well as in one of the truncated cone-like bowls and in two jars, some peculiar depression features were identified, which could be observed in approximately horizontal alignments and in proximity to the coil-joins (Figure 5). They can be interpreted as finger prints left by the potter by pressing the wall of the vessel while fixing one coil to the other; based on their frequency in the analysed sample, these finger marks can possibly be referred to as an example of *kinaesthetic knowledge*<sup>12</sup>.

Moreover, the visual observation of the fractures showed that the last coil, namely the one used to

form the rim of the vessels, was clearly shorter than the other coils forming the pot. To highlight this trend, some simple Excel line graphs were made (Figure 6): the height of the last coil (rim coil) of each vessel was compared to the height of one coil from the body of the same vessel<sup>13</sup>. As can be observed, a significant difference can be noticed between the body- and the rim-coils. More precisely, the rim-coil is generally in a one third ratio to the body-coil. This can be observed in many sherds, regardless of their shape, so that the use of a smaller coil for the rim of the vessels seems to reflect an important operative habit in the forming process. More interestingly, the rim often seems to have been formed through the addition of a small coil in some vessels made by

<sup>12</sup> In the sense of Wendrich (2006; 2012) and Miller (2007).

<sup>13</sup> In the cases where more than one coil was detected in the body of the vessel, an average value was considered.

moulding or slab-building too<sup>14</sup>. The use of a smaller coil for the rim therefore seems to have been an operative procedure for vessels which were not made by coiling.

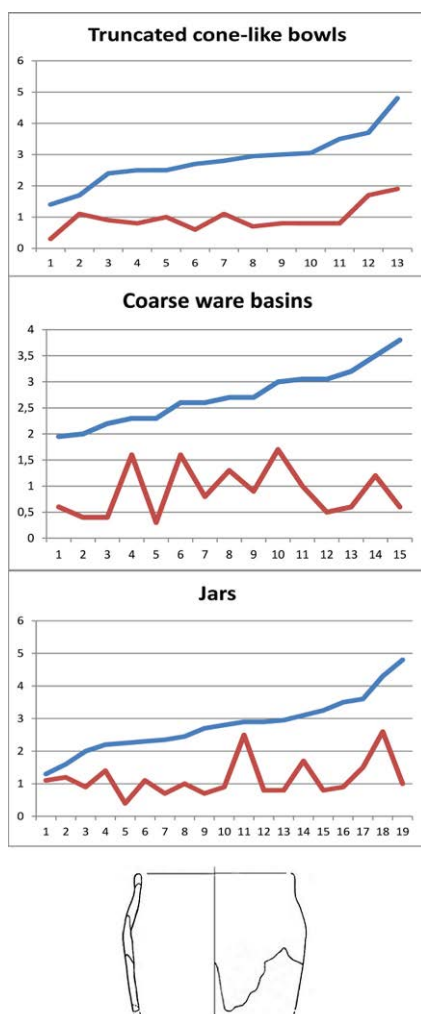


Figure 6. Excel line graphs representing the heights of the coils for the three considered morphological groups. The blue lines represent the heights of the coils of the vessels' body, whereas the red lines represent the heights of the corresponding rim coils. Below, an example of a jar: the coil used to form the rim is very clearly smaller than the others.

### The dimensional and statistical study of coiling

The analysis of coiling was extended in order to understand whether the production and the assembly of the coils followed specific operative rules or could alternatively be considered non-standardised operations<sup>15</sup>. To this purpose, the height<sup>16</sup> and the

<sup>14</sup>This was detected in seven slab-built vessels and in four vessels formed by moulding.

<sup>15</sup>The statistical study was conducted by Luca Bondioli (Pigorini National Museum of Prehistory and Ethnography, Rome).

<sup>16</sup>The height of the coils is referred to as the distance between one joint and the other, after the assembly of the coils and all the transformation processes they undergo in the phases of refining,

thickness<sup>17</sup> of 116 coils were measured, taking into account the truncated cone-shaped bowls, the large basins, the jars and the large coarse ware jars, considering the results of the visual observation and of the X-radiography. In the first place, these variables were examined in order to understand whether the dimensions of the coils were in any way determined by the shape of the vessel to be formed (Figure 7); secondly, the correlation between the variables themselves (height and thickness) was considered (Figure 8).

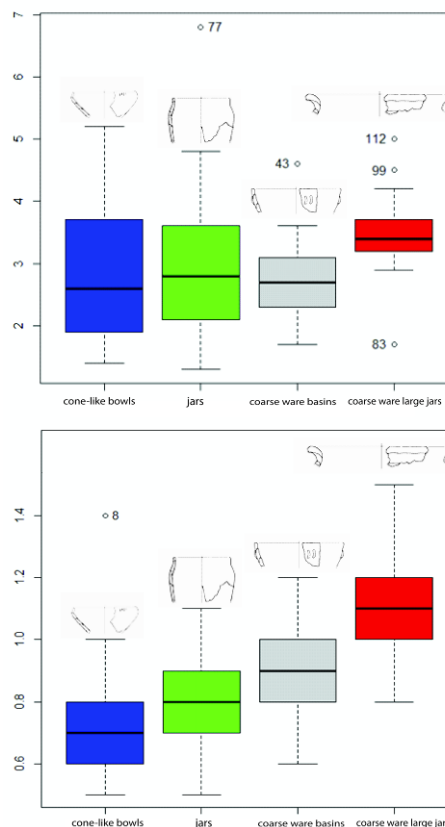


Figure 7. Box-plots describing the height (upper) and thickness (lower) of the coils of the four morphological groups considered for the statistical analysis. The values of the height and of the thickness are expressed in centimetres on the vertical axes. The numbers in the plots are the identification numbers of single sherds whose coils' height and thickness do not fit in the range expressed by the boxes and are thus to be considered exceptions.

drying and firing. The coils used for the rims were not considered in the statistical study, because, as shown before, they often are remarkably smaller than all the other ones. Two distortive elements must be mentioned with regard to the measurement conditions: 1) the height of the coils was measured in a straight line and not following the curve profile of the vessels, which can make some bigger coils appear shorter; 2) when the joints were very stretched, a medium point along them was considered the limit of the coil.

<sup>17</sup>The thickness of the coil is referred to as the thickness of the wall of the vessel measured in the range between two joints. In most cases, the thickness does not vary much in the interval of a coil, but in the cases where the variation was more than 2 mm a median value was considered.



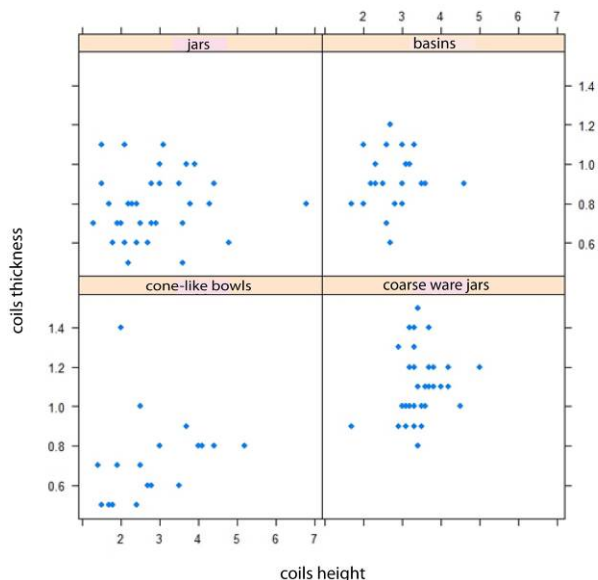


Figure 8. Scatter plots describing the statistical correlation between the height and the thickness (expressed in centimetres) of the coils in the four different morphological groups. As can be observed, the data points show that no correlation is detectable between the two data sets.

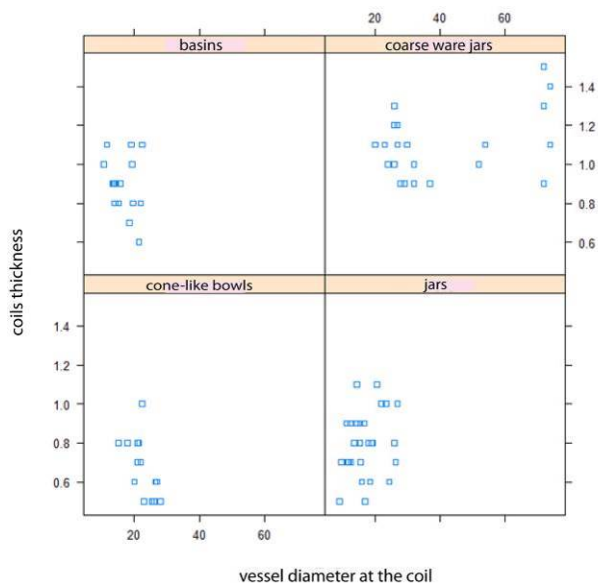


Figure 9. Scatter plot comparing the thickness of the coils to the diameter of the vessels (as defined in the text). No correlation is evident, except in the case of the cone-like bowls, for which the Pearson's R correlation coefficient between the traits is significantly different from zero ( $p < 0.01$ ).

Later on, another variable, the diameter of the vessel measured at the coil<sup>18</sup>, was taken into account with the specific purpose of verifying the hypothesis of a possible correlation between the diameter of the vessel and the thickness of the coils (Figure 9). The

<sup>18</sup> This value is referred to as the diameter of the vessels, measured in the insides and at a medium point along the height of the coils. This was chosen as a more representative value than the diameter of the rims, as this latter often varies in consideration of the shape of the rim itself.

constant ratio/correlation between the variables possibly reveals the use of some constant guiding criteria in the production of the coils and consequently some degree of standardisation in the production process. More precisely, a direct or inverse proportionality as well as the absence of any correlation between the variables possibly reflects a processual meaning, as is shown in the following hypothetical-deductive diagram (Figure 10).

The results of the statistical analysis show an almost complete lack of correlation between the variables. In other words, the coils seem to have been made with regard neither to the kind of vessel to be formed nor to specific topological considerations. Only one exception needs to be mentioned: in the morphological group of the truncated cone-like bowls an inverse proportionality can be observed between diameter of the vessels and thickness of the coils and of the walls. As thinner walls are generally characteristic of more refined vessels, then this evidence could implicate that largest vessels, namely those with wider diameter, were given greater attention in regard to quality and refinement, possibly because they were used for communal drinking and therefore connected with social practices of status-display.

### Identification of the paddle-and-anvil technique

Studying the morphological group of the bowls, it was noticed that in some sherds the thickness of the walls remained nearly constant (which is generally an indicator of the use of coils), whereas in other sherds the thickness of the walls varied remarkably. In particular, the thickness would progressively reduce proceeding from the rim to the foot and in some cases would even get to a minimum of 2 mm at the foot (Figure 11). The hypothesis formulated to explain this evidence was that the vessels with such a variability in the wall thickness had possibly been treated with the paddle-and-anvil technique, and this was actually sustained by the observation of stress lines in the fractures, namely of micro-ridges and micro-depressions visible in lines running parallel to the wall surface. To verify this hypothesis a number of bowls were selected, all having comparable preservation conditions. For each bowl the length of the sherd was divided into 5 equally spaced units<sup>19</sup> and the thickness of the wall was measured in 6 different equally spaced points, namely at the 0%, 20%, 40%, 60%, 80% and 100% of the length of the sherd. In this way it was possible to quantify the variation of the wall thickness in the different sherds

<sup>19</sup> Five measurements is an arbitrary number, chosen to get a sufficient but not unnecessary number of measurements.



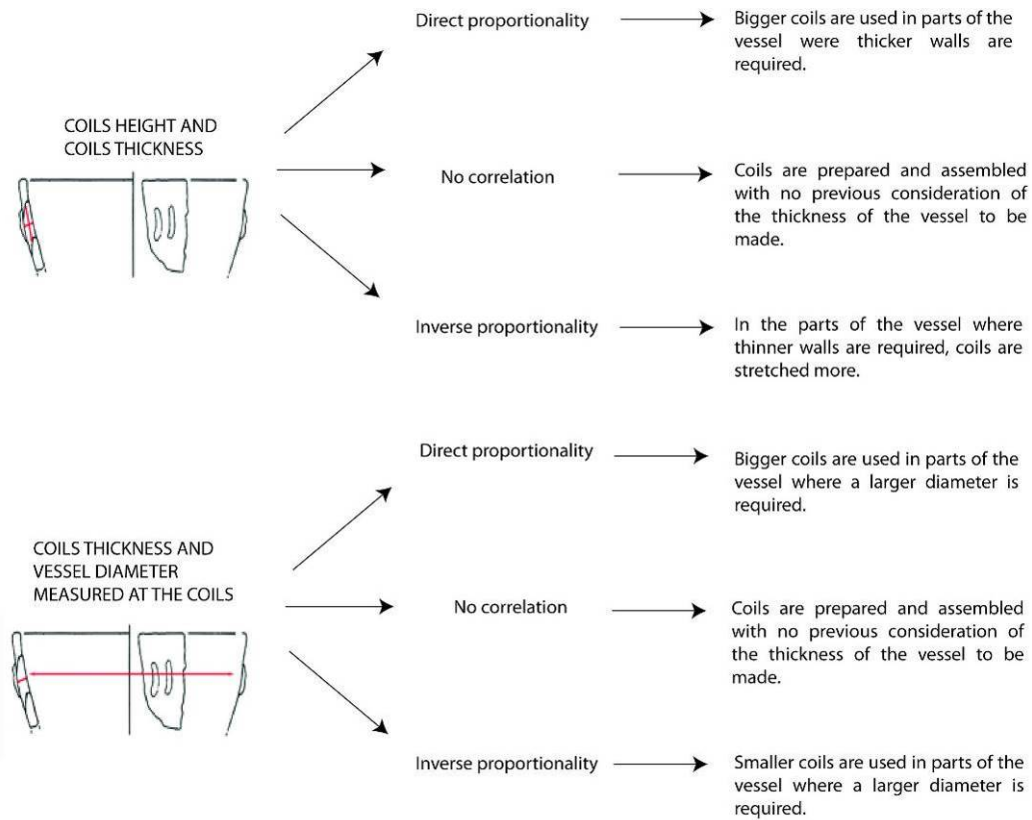


Figure 10. Hypothetical-deductive diagram showing the processual interpretation of the statistical correlation or its absence between the variables.

and to point out two trends: on one hand, the bowls that clearly showed a reduction of the wall thickness also had stress lines in the fractures; on the other hand, bowls whose wall thickness remained constant did not have stress lines in the fractures (Figure 12)<sup>20</sup>. Thus, for the first time in pottery technology studies focusing on Italian Iron Age, the paddle-and-anvil technique could be empirically identified.

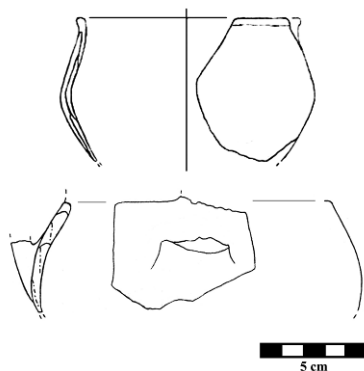


Figure 11. Drawings of two bowls whose wall thickness gradually reduces proceeding from the rim to the foot. The bowl above is formed by slab-building, whereas the one below is formed by coiling, with evidence of stress-lines, indicated by dash-dot lines.

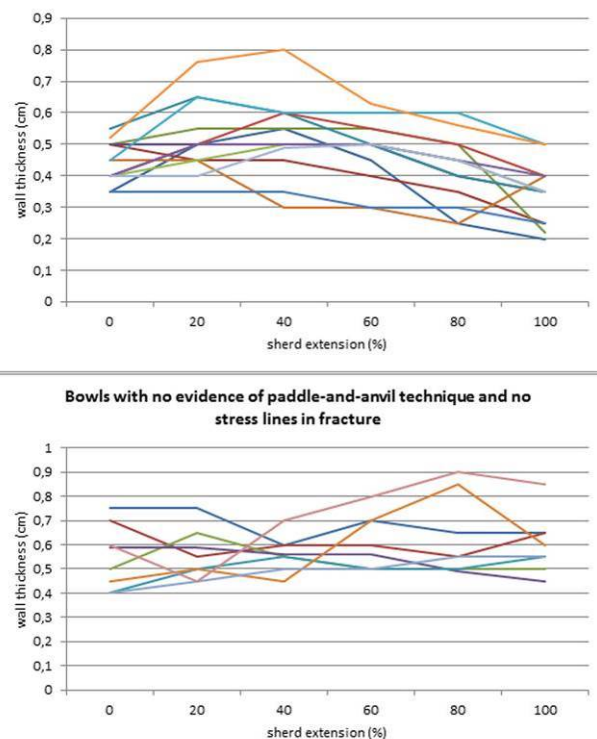


Figure 12. Line chart that shows the variability of the wall thickness of the studied bowls. Upper, bowls for which the use of the paddle-and-anvil technique had been identified; lower, bowls, which are unlikely to have been made by this technique. Each different line in the chart represents a single sherd.

<sup>20</sup> Out of 20 analysed sherds, only three contradict this trend.

In many cases the rim of the bowls was so tiny that the use of a pebble on the inside of the vessel, commonly referred to for describing the paddle-and-anvil technique, would have been impossible. Therefore it seems more likely that the walls would have been made so thin by putting the bowls upside down on a rod-shaped anvil, obliquely fixed in the ground (Figure 13).

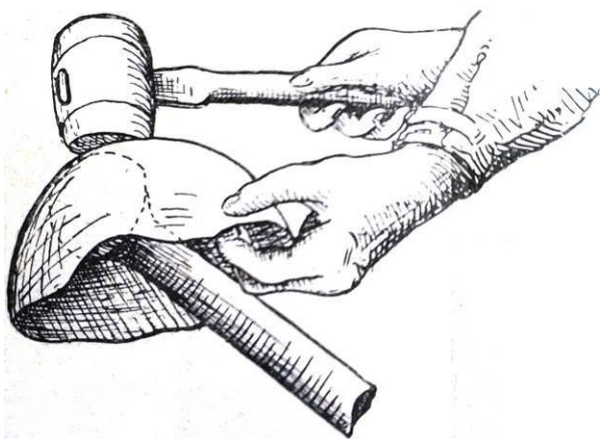


Figure 13. Illustration of the beating procedure of a copper sheet on a rod-shaped anvil to make a bowl. The figure is taken from an Italian 1926 handbook for industrial workers and apprentices (Massenz 1926, 158). Interestingly the illustrated procedure looks very similar to the techniques deployed in ancient Greece (see Figure 14).

This technique is documented for the production of metal bowls and more specifically of bronze helmets in Greece in the archaic and classic period, as shown by a pyxis from the Petit Palais in Paris, Dutuit Collection, and dated to the last two decades of the 6<sup>th</sup> century BC, and by a bronze figurine from the Metropolitan Museum of Art (1985) (Figure 14).

### The diachronical study of the techniques

Once the forming techniques were identified (Table 1), a chronological study was undertaken in order to identify any technical change across the *ca.* two centuries long life of the site. As already mentioned, the stratigraphy of the site did not help to provide a chronology of the materials; thus the sherds were dated exclusively on a typo-chronological basis<sup>21</sup>.

<sup>21</sup> The PhD study by Silvia Rossi (University of Padua) served as the base for the diachronical study of the pottery technology at Erbè. The typo-chronology elaborated by Rossi (2008) was critically reviewed by checking the most significant works on pottery typo-chronology of the period (Peroni 1975; Capuis and Chieco Bianchi 1985; Capuis and Chieco Bianchi 2006; De Min *et al.* 2005) and also by taking into account more recent bibliography (Gamba *et al.* 2014; Ruzzante 2016).



Figure 14. Upper, bronze figurine dated between the end of the 8<sup>th</sup> and the beginning of the 7<sup>th</sup> century BC, of unknown provenance and displayed at the Metropolitan Museum of Art, New York. The right hand the craftsman must have held an instrument that is not preserved, possibly a hammer (from *The Metropolitan Museum of Art Bulletin* 1985, 43(2)). Lower, Greek pyxis with picture of a young craftsman creating a metal helmet by beating it on an anvil in the shape of a rod, obliquely fixed in the ground (Dutuit Collection, Petit Palais, Paris; from Vidale 2002, 186).

As a result of the diachronical study of the techniques, a substantial differentiation can be traced between “functional” vessels on one hand, used in the everyday life for practical purposes, and more elaborate vessels on the other hand. Coiling, slab-building and moulding are techniques that possibly had a much longer life than the site itself: they started to be used long before the 8<sup>th</sup> century and did not disappear in the Veneto region after Erbè was abandoned. These techniques were present for the entire life period of the site and did not evolve in any way in the site between the 8<sup>th</sup> and the 6<sup>th</sup> century BC.

The same cannot be said for the paddle-and-anvil technique and for the use of the potter's wheel. The paddle-and-anvil technique was also known in the earliest phases of occupation of the site; however, its frequency changed remarkably with the time. The technique was namely identified in the 33% of the 8<sup>th</sup> century bowls, whereas its use increased to the 76% in the 7<sup>th</sup> century<sup>22</sup>.

With regard to wheel-throwing, very little is known about its introduction in the Veneto region, which should have occurred during the life period of Erbè<sup>23</sup>. Among the analysed sherds, only 12 could possibly have been refined using a wheel and none of them can be dated to the 8<sup>th</sup> century. The identification of the technique remains problematic, but it is sure that it was used in Erbè only as a secondary technique, namely for the refinement of the vessels, and not to form them.

Thus, according to the diachronic study of the pottery technology in Erbè, from the 7<sup>th</sup> century some significant changes seem to have occurred in relation to an intensified need for more refined vessels, beaten through the paddle-and-anvil technique and re-shaped through the use of the wheel.

## Discussion and conclusion

First of all, a methodological issue must be addressed. Although only a relatively small number of sherds could be analysed through X-radiography (23 out of 127), the results of the X-ray analysis confirm to a great extent the hypotheses made through visual observation. In fact, the two methods gave contrasting results regarding the forming techniques in only three cases; in 12 other cases, some minor differences were observed, such as the number of coils or the position of the joints. Generally speaking, X-ray analysis seems a more accurate method for the identification of the primary forming techniques, as it often showed a greater number of coils or allowed a more precise identification of the joints. Coiling, in particular, often showed in radiographs through the presence of horizontal stripes, alternatively darker (joints) and brighter (coils). To this respect, we used a yellow line to indicate joints (see Figure 5) even if the joint itself could not really be described as a distinct line but rather as an area or, as said above, a darker stripe. Only in some cases, when the coils were not well

joined to each other, the limit between them was more clearly identifiable through a linear void and thus as a line. Conversely, the more accurately the pot was made, the more difficult it is to identify the forming techniques. In the cases when, for example, vessels made by coiling were possibly refined through the use of the potter's wheel, the typical alternation of darker and brighter areas is not clearly visible on radiographs. X-radiography seems in general less reliable (or more difficult to interpret) with regard to the study of secondary forming procedures like the paddle-and-anvil technique, which in our sample has never been identified through X-rays<sup>24</sup>. Stress lines in sections, for example, are not visible in radiographs, even if this may depend on the fact that radiographic images show the front side and not the section of the sherds. Regardless, the match between the two modes of observation was on the whole fairly positive, supporting the validity of visual observation.

Coiling seems to have been the most common and versatile technique. In this regard, the statistical analysis of the coils' dimension suggested an essentially non-standardised production process<sup>25</sup>, in which coils should have been prepared and assembled regardless of the shape of the vessel to be formed. However, some kind of operative rules could also be observed, such as the use of a smaller coil for the rim and the habit of shaping and stabilising the vessel walls by regular movements of the fingers. In general, the complexity of the production processes must be emphasised, as different techniques were very often applied together for the production of a single vessel. Even very "simple" basins made by slab-building, for instance, often have their rim made by a single little coil, and it is common to find that different techniques are combined and associated, as in the case of vessels made by coiling and successively wheel-shaped and treated with the paddle-and-anvil technique. In this respect, every technique is much easier to detect when it is the only one to have been used in a vessel; studying experience shows instead that the identification of the forming technique(s) is often rather problematic (see also Berg 2011b).

With regard to the paddle-and-anvil technique in Iron Age northern Italy, this study could contribute to a better definition of its diagnostic characteristics, which can be summarised as follows:

- Tendency of the vessels' wall to get progressively thinner from the rim to the foot. A minimum of 2

<sup>22</sup> The percentage values are calculated on a relatively low number of sherds (22), so that they should not be considered deeply indicative of a trend.

<sup>23</sup> Capuis 1993, 110; Gamba *et al.* 2013, 207; Chicco Bianchi and Tombolani 1988, 72.

<sup>24</sup> Berg (2008, 1184-1185) has addressed the question of the visibility of the secondary modification techniques (like burnishing, polishing and smoothing): none of these seem to be visible radiographically.

<sup>25</sup> Blackman *et al.* 1993.



mm can be achieved in the case of small bowls, which implicates a high degree of technical skills;

- The presence of stress lines in fractures, namely of micro-ridges, and micro-depressions visible in lines running parallel to the wall surface, which can be interpreted as the result of the pressure put on the walls by the technique<sup>26</sup>.

The paddle-and-anvil technique being a secondary forming technique, its diagnostic characteristics are going to be observed on sherds together with other features related to the primary forming technique(s) involved. Therefore, an identification of the forming techniques based on the parameters listed in Table 1 is still valid also for vessels that were later treated with the paddle-and-anvil technique. The only parameter that seems to be affected by the paddle-and-anvil technique is the thickness of the walls.

Moreover, the research into the paddle-and-anvil technique highlights the technological proximity between pottery production and metallurgy in Iron Age Veneto. This can be observed from the 9<sup>th</sup>-8<sup>th</sup> century BC, when the specific pottery shape of the *situliformi*, or inverted-truncated cone-like restricted vessels, clearly imitating the shape of bronze buckets, appeared in the region<sup>27</sup>. Very often, and particularly from the 8<sup>th</sup> century, these vessels were decorated by burnishing, with a shiny effect that gives the appearance of metal surfaces. Moreover, the application of metal studs and of tin sheet on the surface of some vessels, which spread across the Veneto region during the 7<sup>th</sup> and 6<sup>th</sup> centuries BC, possibly indicates that a real collaboration between potters and smiths was actually put into action. The study of the ceramic sherds from Erbè confirms the existence of a strong relationship between pottery technology and metalworking: in this regard the hypothesis of a beating procedure that clearly imitates the planishing of metal objects matches the general picture of a technical environment characterised by the lack of absolute divisions between technical fields. The concept of *technical continuity*, as expressed by Leroi-Gourhan (1945, 344), shall therefore be considered important for the interpretation of the connection between pottery technology and metalworking: according to this view, no invention is possible *ex-nihilo*, but invention itself is the result of combination and reproduction. In this respect, the idea of technical domains as strictly separated fields reflects a modern way of categorising reality which is probably unsuitable for explaining the

dynamicity, the continuity of ancient production systems.

As shown by the diachronical study of the techniques, some significant changes seem to have taken place around the early 7<sup>th</sup> century BC in Erbè, and probably in the Veneto region as a whole. These changes were the introduction of the wheel for the secondary modification of some vessels (bowls, *situliformi* and small refined jars) and the intensification of the use of the paddle-and-anvil technique for the specific production of refined vessels (especially bowls) with particularly thin walls. Moreover, also some changes regarding the surface treatments must be added, although they are not the focus of this study: the use of burnishing, with an intense shiny effect, and the application of metal studs on the surfaces of some vessels (especially bowls and *situliformi*) visibly increased in the 7<sup>th</sup> century BC. It must be noted that none of these changes clearly implicated a functional or practical improvement, but all of them required increased skills and energy with the exclusive purpose of producing more refined vessels. In other words, a great surplus of work was apparently demanded, which is characteristic of the production of prestige-objects<sup>28</sup>. This, together with the fact that the new techniques were not applied to all kinds of shapes but only to bowls, *situliformi* and tiny fine ware jars, points to a technological innovation that was mainly pushed by new needs for status-display.

Thus, the technological innovation that took place around the 7<sup>th</sup> century BC in Erbè (and probably in the whole polity of the ancient Veneto region) possibly reflects the emergence in peripheral centres of social groups which aimed for representing themselves through refined vessels, probably emulating the elites of Padua and Este and certainly demanding from craftspeople improved skills and a greater amount of work.

### Acknowledgments

I wish to acknowledge the help and the support provided by my supervisors, Massimo Vidale and Giovanni Leonardi (University of Padua, Italy). I am thankful also to Luca Bondioli (Pigorini National Museum of Prehistory and Ethnography, Rome) whose advice was extremely useful for the statistical study of the techniques, and to Carlo Rettore (Radiology Department at the Hospital in Cittadella, Padua), Giuseppe Salemi and Emanuela Faresin (University of Padua), who supported me with the X-ray analysis.

<sup>26</sup> The other variables to consider to identify the forming techniques, namely the symmetry, the orientation and position of the fractures and so on, will depend on the primary forming technique.

<sup>27</sup> See contribution of Vidale 2013.

<sup>28</sup> Giannichedda 2006.

## References

- Berg, I. 2008. Looking through pots: recent advances in X-radiography. *Journal of Archaeological Science* 35, 1177-1188.
- Berg, I. 2009. X-Radiography of Knossian Bronze Age Vessels: Assessing our Knowledge of Primary Forming Techniques. *Annual of the British School at Athens* 104, 137-173.
- Berg, I. 2011a. Exploring the *chaîne opératoire* of ceramic through X-radiography. In Scarcella, S. (ed.), *Archaeological Ceramics: A Review of Current Research*. BAR International Series S2193. Archaeopress, Oxford.
- Berg, I. 2011b. What's in a forming technique? An Investigation into Wheel-throwing and Wheel-coiling of Bronze Age Crete. *The Old Potter's Almanack* 16, 9-12.
- Bettinardi, I. 1996-7. *L'abitato protostorico di Castion di Erbè (VR): gestione informatica dei dati (dallo scavo al reperto) e tipocronologia della produzione vascolare (2<sup>nd</sup> lotto)*. Tesi di Laurea. Università degli Studi di Padova.
- Bettinardi, I. and Leonardi, G. 2002. Gestione e analisi informatizzata dei dati dell'abitato arginato di Castion di Erbè. In Peretto, C. (ed.), *Analisi informatizzata e trattamento dei dati delle strutture di abitato di età preistorica e protostorica in Italia*, 287-302. Pisa.
- Blackman, M. J., Stein, G. J. and Vandiver, P. 1993. The standardization hypothesis and ceramic mass productions: technological, compositional and metric indexes of craft specialization at Tell Leilan, Syria. *American Antiquity* 58, 60-80.
- Burrigato, F., Grubessi, O. and Lazzarini, L. (eds). 1994. *1st European Workshop on Archaeological Ceramics. Ricerche Archeometriche e Studi Archeologici sulla Ceramica Antica*. Roma.
- Capuis, L. and Chieco Bianchi, A. 1985. *Este I. La necropoli di casa di Ricovero. casa Muletti Prosdocimi e casa Alfonsi*. Roma.
- Capuis, L., Leonardi, G., Pesavento Mattioli, S. and Rosada, G. 1990. *Carta archeologica del Veneto*. Modena. Volume II, 184-185.
- Capuis, L. and Chieco Bianchi, A. 2006. *Este II. La necropoli di villa Benvenuti*. Roma.
- Capuis, L. 1993. *I Veneti. Società e cultura di un popolo dell'Italia preromana*, Longanesi.
- Carr, C. 1990. Advances in Ceramic Radiography and Analysis: Application and Potentials. *Journal of Archaeological Science* 17, 13-34.
- Carr, C. 1993. Identifying Individual Vessels with X-Radiography. *American Antiquity* 58, 96-117.
- Carr, C. and Komorowski, J. C. 1995. Identifying the mineralogy of rock temper in ceramics using X-radiography. *American Antiquity* 60, 723-749.
- Carr, C. and Riddick, E. B. J. 1990. Advances in Ceramic Radiography and Analysis: Laboratory Methods. *Journal of Archaeological Science* 17, 35-66.
- Cazzella, A., Desogus, P., Levi, S. T. and Vidale, M. 1994. Applicazioni di tecniche xeroradiografiche allo studio della ceramica dell'età del bronzo. In Burrigato, F., Grubessi, O. and Lazzarini, L. (eds), *1st European Workshop on Archaeological Ceramics. Ricerche Archeometriche e Studi Archeologici sulla Ceramica Antica*, 415-420. Roma.
- Chieco Bianchi, A. M. 1985. *Il Museo Nazionale Atestino di Este*. Editoriale Programma.
- Chieco Bianchi, A. M. and Tomboliani, M. 1988. *I paleoveneti. Catalogo della mostra sulla civiltà dei Veneti antichi*. Editoriale Programma.
- Courty, M. A. and Roux, V. 1995. Identification of wheel throwing on the basis of surface features and microfabrics. *Journal of Archaeological Science* 22, 17-50.
- Cuomo di Caprio, N. 2007. *Ceramica in archeologia 2*. Roma.
- De Min, M., Gamba, M., Gambacurta, G. and Ruta Serafini, A. (eds). 2005. *La città invisibile*. Bologna.
- Ellingson, W. A., Vandiver, P., Robinson, T. K. and Lobick, J. J. 1998. Radiographic Imaging Technologies for Archaeological Ceramics. In Sayre, E. V., Vandiver, P., Druzik, J. and Stevenson, C. (eds), *Material Issues in Art and Archaeology* 123, 25-32.
- Favero, M. 1994-5. *L'abitato protostorico di Castion di Erbè (VR): materiali e funzione*. Tesi di Laurea. Università degli Studi di Padova.
- Gamba, M., Gambacurta, G., Ruta Serafini, A., Veronese, F. and Tinè, V. 2013. *Venetkens. Viaggio nella terra dei Veneti antichi*. Venezia.
- Gamba, M., Gambacurta, G. and Ruta Serafini, A. (eds). 2014. *La prima Padova. Le necropoli di palazzo Emo Capodilista-Tabacchi e di via Tiepolo-via san Massimo tra il IX e l'VIII secolo a. C.* Regione del Veneto.
- Giannichedda, E. 2006. *Uomini e cose. Appunti di archeologia*. Bari.
- Hayden, B. 1998. Practical and Prestige Technology: The Evolution of Material Systems. *Journal of Archaeological Method and Theory* 5, 1, 1-55.

- Lang, J. and Middleton, A. 2005 (eds). *Radiography of Cultural Material, 2<sup>nd</sup> edition*. Butterworth-Heinemann, Oxford.
- Leonardi, G. 1975a. Castion di Erbè (Prov. di Verona). *Rivista di Scienze Preistoriche* XXX, 377-378.
- Leonardi, G. 1975b. Castion di Erbè (Verona). *Preistoria Alpina* 11, 337-338.
- Leonardi, G. 1976a. Castion di Erbè (Verona). *Aquileia Nostra* XLVII, 262.
- Leonardi, G. 1976b. Castion di Erbè (Com. di Erbè) (Verona). *Studi Etruschi* XLIV, 412.
- Leonardi, G. 1977. Castion di Erbè (prov. Di Verona). *Rivista di Scienze Preistoriche* XXXII, 326.
- Leonardi, G. 1979. Castion di Erbè (Com. di Erbè – Verona). *Studi Etruschi* XLVII, 483.
- Leonardi, G. 2002. Castion di Erbè. Aspes A. (ed.), *Preistoria veronese. Contributi e aggiornamenti. Memorie del Museo Civico di Storia Naturale di Verona*. Verona.
- Leroi-Gourhan, A. 1945. *Milieu et techniques*. Paris.
- Levi, S. 2010. *Dal coccio al vasaio. Manifattura, tecnologia e classificazione della ceramica*. Bologna.
- Mannoni, T. and Giannichedda, E. 1996. *Archeologia della produzione*. Torino.
- Massenz, A. 1926. *Il calderaio moderno. Manuale ad uso teorico pratico dei calderai, capi officina, alunni delle scuole industriali, piccole industrie*. Ulrico Hoepli Editore. Milano.
- Miller, H. M. L. 2007. *Archaeological Approaches to Technology*. San Diego.
- Peroni, R. 1975. *Studi sulla cronologia delle civiltà di Este e Golasecca*. Firenze.
- Rice, P. M. 1987. *Pottery Analysis: A Sourcebook*. University of Chicago Press. Chicago.
- Rossi, S. 2008. *L'abitato arginato di Castion di Erbè (VR) alla luce dei risultati dello studio tipocronologico della ceramica vascolare e considerazioni sulla prima età del Ferro nel territorio veronese*. Tesi di Dottorato. Università degli Studi di Padova.
- Ruzzante, M. 2016. *Il sito di Riviera Ruzzante-angolo Santa Chiara a Padova. Studio tipo-cronologico delle ceramiche delle prime fasi dell'età del Ferro*. Tesi di laurea. Università degli Studi di Padova.
- Rye, O. S. 1977. Pottery Manufacturing Techniques: X-ray Studies. *Archaeometry* 19, 205-211.
- Rye, O. S. 1981. *Pottery Technology. Principles and Reconstruction*. Washington.
- Tite, M. S. 2008. Ceramic production. provenance and use – a review. *Archaeometry* 50, 2, 216-231.
- Toscani, L. 1995-6. *L'abitato protostorico di Castion di Erbè (VR): il materiale della Capanna 11*. Tesi di Laurea. Università degli Studi di Padova.
- Vandiver, P. and Tumosa, C. S. 1995. Xeroradiographic imaging. *American Journal of Archaeology* 99, 121-124.
- Vandiver, P., Ellingson, W. A., Robinson, T. K., Lobick, J. J., Séguin, F. K. 1991. New applications of X-radiographic imaging technologies for archaeological ceramics. *Archaeometry* 5, 185-207.
- Vandiver, P. and Wheeler, G. S. 1991. *Introduction to Material Issues in Art and Archaeology*. In Vandiver, P., Druzik, J. and Wheeler, G. S. (eds), *Material Issues in Art and Archaeology* 185, XVII-XXVI. Material Research Society Symposium Proceedings. Pittsburgh.
- Vidale, M. 1992. *Produzione artigianale protostorica. Etnoarcheologia e archeologia*. Padova.
- Vidale, M. 2002. *L'idea di un lavoro lieve. Il lavoro artigianale nelle immagini della ceramica greca tra VI e IV secolo a.C.* Padova.
- Vidale, M. 2007. *Ceramica e archeologia*. Roma.
- Vidale, M. 2013. *Tra fornaci e mantici: il mondo degli artigiani*. In Gamba, M., Gambacurta, G., Ruta Serafini, A., Veronese, F. and Tinè V. (eds), *Venetkens. Viaggio nella terra dei Veneti antichi*. Venezia.
- Wendrich, W. 2006. Body knowledge. ethnoarchaeological learning and the interpretation of ancient technology. In Mathieu, B., Meeks, D. and Wissa, M. (eds), *L'aort de l'Egypte a l'Histoire des Techniques. Methodes. Chronologie et Comparaisons*. Institut Francais d'Archeologie Orientale. Biblioteque d' Etude 142, 267-75.
- Wendrich, W. 2012. *Archaeology and Apprenticeship: Body Knowledge. Identity. and Communities of practice*. Tucson.
- Zanichelli, 1999. *Atlante Geografico*. Bologna.



## IMPRESSED VESSEL BOTTOMS FROM ȘOIMUȘ-LA AVICOLA (FERMA 2), HUNEDOARA COUNTY, ROMANIA

Cristian Eduard Ștefan

“Vasile Pârvan” Institute of Archaeology, Romanian Academy, Henri Coandă str., No. 11, Bucharest  
Email: [cristarh\\_1978@yahoo.com](mailto:cristarh_1978@yahoo.com)

### Introduction

Between 16 August and 16 November 2011, during the construction of the A1 Motorway, the segment located between Deva and Orăștie, a joint team of archaeologists from the “Vasile Pârvan” Institute of Archaeology (Bucharest), the Roman and Dacian Civilization Museum (Deva) and the Romanian National History Museum (Bucharest) conducted preventive excavations in the settlement of Șoimuș. The settlement is positioned in the Șoimuș commune, between this locality and Bălata Village (Hunedoara County), at *La Avicola (Ferma 2)*, on the first terrace of the Mureș river (East-West direction). On the maps of the Military Topographic Department from the 1970s, the place where the settlement was researched is called *Dumbrava* (Ștefan 2014, 14, figs. 1 and 2).

Considering the size and archaeological complexity of the excavations, the site was divided into two sectors: “zone A”, the Eneolithic core, investigated by the specialists of the Bucharest institutions, and “zone B”, a Bronze Age settlement, investigated by the specialists of the Deva Museum. From “zone A” *ca.* 700 features were identified, most of them belonging to the Neolithic, but also to the Bronze Age, Roman, post-Roman and the early Medieval periods (for further details, see Petcu *et al.* 2012, 291-292; Ștefan *et al.* 2013, 49-66; 2015, 183-209; 2016, 171-189; Ștefan 2014, 14-22; 2016, 31-66; Niță *et al.* 2015, 97-116; Ștefan and Petcu 2015, 117-126; Dobrescu *et al.* 2016, 45-56; Mărgărit *et al.* 2016, 363-397).

In this contribution we present the analysis of some vessel bottoms from Șoimuș which bear traces of vegetal imprints, in order to understand what type of plants were used, in which form and why the Neolithic potter(s) carried out this kind of procedure. These vessels represent *ca.* <1% of the ceramic assemblage. We also present the results of a small-scale experiment to imprint weave patterns on clay.

### Artifacts and contexts

Seventeen pot bottom fragments were selected for analysis, all of them bearing traces of vegetal

imprints. Some of them have a very clear pattern of the vegetal weave (e.g. see Figures 1, 4 and 16).

1) Pot fragment with impressed bottom, sand- and rock-tempered, semifine fabric and red-brick colour (Figure 1).



Figure 1. Șoimuș-La Avicola (Ferma 2): impressed vessel bottom from Feature 181 (photo R. Petcu). Insert: location map of the site area.

It was recovered from Feature 181 - a pit with dimensions of 1.8 x 3.9 m and a maximum depth of 0.6 m. It contained pottery and animal bones, had an elongated oval shape and its infill consisted of a brown-greyish soil mixed with ash pigments, daub and yellow clay (Figure 2).

2) Pot fragment with impressed bottom, sand- and rock-tempered, coarse fabric and red-brick colour (Figure 3). It was recovered from Feature 239 which is a ditch with a length of 54 m, a maximum width of 4.1 m and a maximum depth of 2.2 m. It was filled with debris, pottery fragments, anthropomorphic figurines, daub with traces of wattle, clay weights,

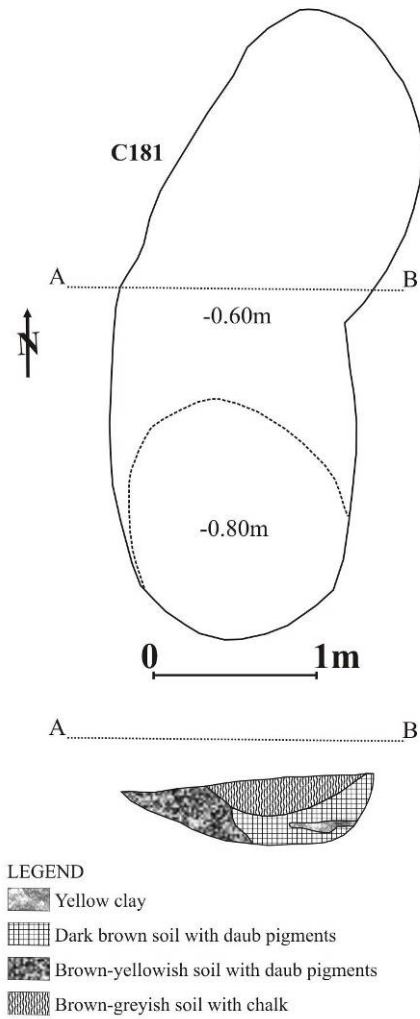


Figure 2. Şoimuş-La Avicola (Ferma 2): Feature 181.

obsidian and flint items, a quern, human bones, animal bones, bone and antler tools, miniature vessels. The ditch was oriented NE-SW, and it had three phases, probably its initial function being for water drainage and after that for enclosing an area or a household (see Ştefan 2014, figs. 16-18).

3) Pot fragment with impressed bottom, sand- and rock-tempered semifine fabric and red-brick colour (Figure 4). It was recovered from Feature 239.

4) Pot fragment with impressed bottom, grog-tempered, coarse fabric and red-brick colour (Figure 5). It was recovered from Feature 353 which is a pit with dimensions of 6.25 × 17.5 m and a maximum depth of 1.6 m. It contained pottery, a clay weight, a strainer, a stone disk, flint and obsidian items, a quern, animal bones and antler tools. After the removal of the vegetal soil, a large area was observed with a brown infill consisting of soil, daub pigment and daub fragments. Due to its irregular shape, the feature may have been a clay extraction pit, later used for the deposition of debris (Figures 6 and 7).



Figure 3. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 239 (photo R. Petcu).

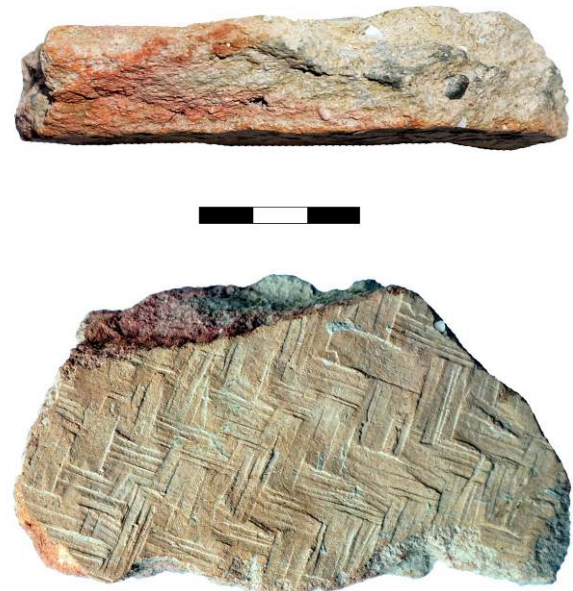


Figure 4. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 239 (photo R. Petcu).







Figure 5. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 353 (photo R. Petcu).



Figure 7. Site of Şoimuş-La Avicola (Ferma 2): Feature 353.

5) Pot fragment with impressed bottom, sand- and rock-tempered, semifine fabric and red-brick colour (Figure 8). It was recovered from Feature 353.

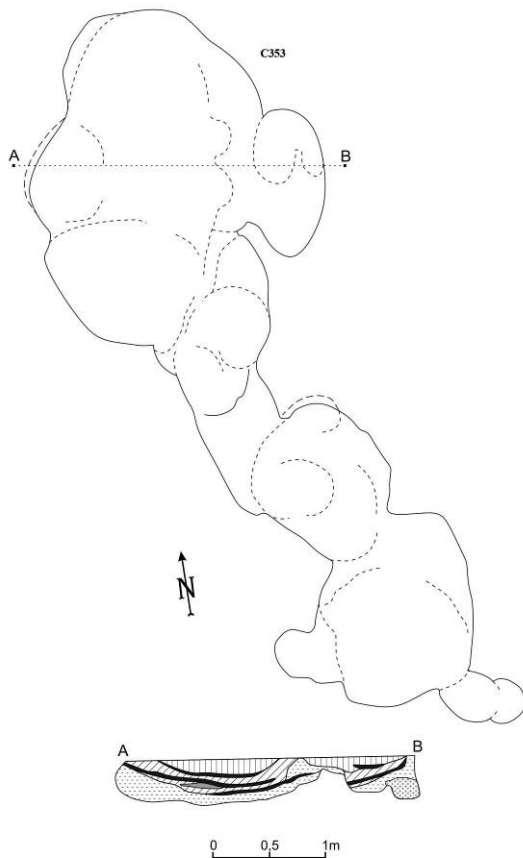

LEGEND

- light brown soil
- brown soil (compact)
- brown soil with ash stripes, charcoal and adobe fragments
- burnt clay stripes and charcoal
- ash stripes
- yellow clay (compact)

Figure 6. Şoimuş-La Avicola (Ferma 2): Feature 353.



Figure 8. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 353 (photo R. Petcu).



6) Pot fragment with impressed bottom, sand- and rock-tempered, semifine fabric and dark red-brick colour (Figure 9). It was recovered from Feature 354 which is a pit with dimensions of  $4.1 \times 7$  m and a maximum depth of 1.3 m. It contained pottery, a clay weight, flint items, a quern, a stone axe, a stone chisel, bone tools and animal bones. The pit is overlapped from north to south by Feature 238 (palisade). The pit had an irregular, ovoid shape and its infill consisted of many layers of burnt materials - charcoal, ash and burnt daub. In the middle of the section a post hole with a diameter of *ca.* 0.5 m was documented, which was filled with dark brown soil mixed with daub pigment. The sides of the pit were indicative of several episodes of deformation and soil collapse (Figures 10 and 11).



Figure 9. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 354 (photo R. Petcu).

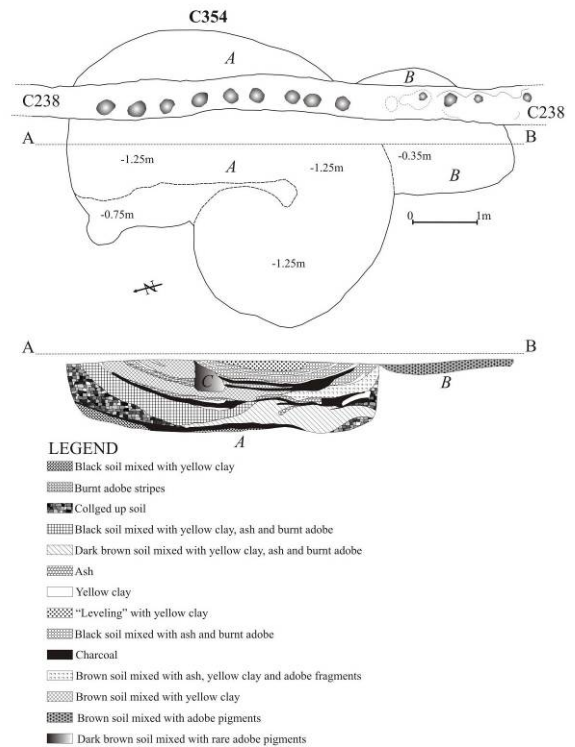


Figure 10. Şoimuş-La Avicola (Ferma 2): Feature 354.



Figure 11. Site photo of Şoimuş-La Avicola (Ferma 2): Feature 354.

7) Pot fragment with impressed bottom, grog-tempered, semifine fabric and red-brick colour (Figure 12). It was recovered from Feature 354.



*Figure 12. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 354 (photo R. Petcu).*

8) Pot fragment with impressed bottom, grog-tempered, coarse fabric and red-brick colour (Figure 13). It was recovered from Feature 354.

10) Pot fragment with impressed bottom, grog-tempered, coarse fabric and dark red-brick colour (Figure 15). It was recovered from Feature 354.



*Figure 13. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 354 (photo R. Petcu).*

9) Pot fragment with impressed bottom, sand- and rock-tempered, coarse fabric and red-brick colour (Figure 14). It was recovered from Feature 354.

11) Pot fragment with impressed bottom, sand- and rock-tempered coarse fabric and dark red-brick colour (Figure 16). It was recovered from Feature 354.



*Figure 14. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 354 (photo R. Petcu).*





Figure 15. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 354 (photo R. Petcu).



Figure 16. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 354 (photo R. Petcu).

12) Pot fragment with impressed bottom, sand- and rock-tempered, semifine fabric and red-brick colour (Figure 17). It was recovered from Feature 444A-B which is a complex of two pits with a maximum depth of 2.7 m. It contained pottery,

anthropomorphic figurines, daub, hearth fragments, flint and obsidian items, a quern, a striker, animal bones, bone tools, antler and shells. Its infill consisted of multiple layers of brown, beige and yellow soil (Figure 18).

13) Pot fragment with impressed bottom, grog-tempered, coarse fabric and dark red-brick colour (Figure 19). It was recovered from Feature 444A-B.



Figure 17. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 444A-B (photo R. Petcu).

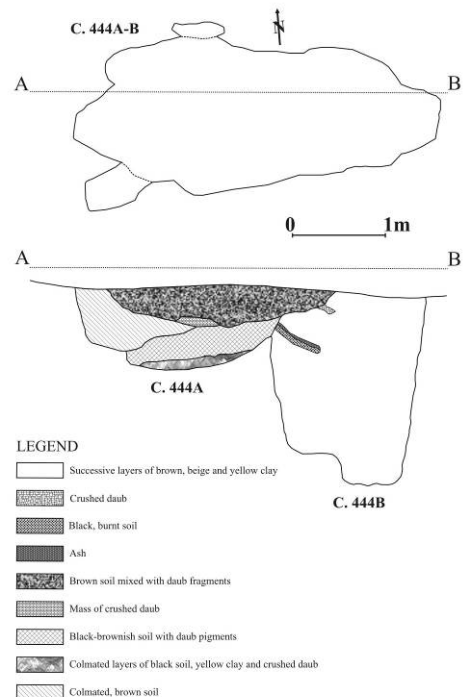


Figure 18. Şoimuş-La Avicola (Ferma 2): Feature 444A-B.



Figure 19. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 444A-B (photo R. Petcu).

14) Pot fragment with impressed bottom, grog-tempered, semifine fabric and dark red-brick colour (Figure 20). It was recovered from Feature 470 which is a pit with dimensions of 1.2 x 1.4 m and a maximum depth of 1.75 m. It contained pottery, hearth fragments, polished tools, bone tools and animal bones. The pit had a circular shape and overlapped Feature 469.



Figure 20. Impressed vessel bottom from Feature 470 (Photo R. Petcu).

15) Pot fragment with impressed bottom, sand- and rock-tempered semifine fabric and red-brick colour (Figure 21). It was recovered from Feature 472 which is a pit with dimensions of 4 x 4.5 m and a maximum depth of 1.45 m. It contained pottery, flint items, a polished stone axe, bone tools, animal bones and antler. The feature had an irregular shape and a few steps at its base. Its infill consisted of successive layers of charcoal and ash in its upper part. Under these layers was a brown-greyish soil mixed with daub, charcoal and ash (Figure 22).



Figure 21. Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 472 (photo R. Petcu).



Figure 22. Şoimuş-La Avicola (Ferma 2): Feature 472.



16) Pot fragment with impressed bottom, grog-tempered, semifine fabric and red-brick colour (Figure 23). It was recovered from Feature 474 which is a pit with a diameter of 3.5 m and a maximum depth of 1.3 m. It contained pottery, zoomorphic figurines, flint items, bone tools, animal bones, unworked antler, and shells. On its southern and eastern sides the pit had steps and further east overlapped Feature 377 and was overlapped by Feature 479. Its infill consisted of a sequence of thin, brown-greyish layers, mixed with lenses of daub, ash and charcoal. On the sides, on its lower part, the infill was brown-greyish with few pigments of charcoal or ashes (Figures 24 and 25).



Figure 23. *Şoimuş-La Avicola (Ferma 2): impressed vessel bottom from Feature 474 (photo R. Petcu).*

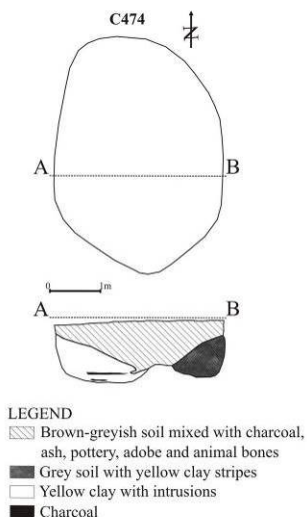


Figure 24. *Şoimuş-La Avicola (Ferma 2): Feature 474.*



Figure 25. *Şoimuş-La Avicola (Ferma 2): Feature 474.*

17) Pot fragment with impressed bottom, sand- and rock-tempered, semifine fabric and red-brick colour (Figure 26). It was recovered from Feature 482 which is a pit with a diameter of 1.6 m and a maximum depth of 0.7 m. It contained pottery, daub, a clay weight and animal bones. Its infill consisted of a dark brown-greyish soil mixed with daub pigments (Figure 27).

### Interpretation and analogies

All 17 vessels can be attributed to the so-called “kitchen ware” and some of them were recovered from grouped features which can possibly indicate special activity areas.

The impressions from the vessel bottoms belong to patterns made by a "weaving method" (two component systems similar to warp yarns from the textile's structure), from vegetal material like rush or reed. The interposing of vegetal elements followed a special rule (so-called stiffened diagonal) which led us to think that Neolithic people knew the mechanical strength of their products (C. Marian pers. comm.). In the samples discussed above, three main clusters were noticed: clear weaving of vegetal matter (see Figures 1, 3, 4, 9, 14, 16, 19, 20, 21, 23); a slightly

different weave, with an oblique pattern (like a rope in profile) (Figure 17); and lightly woven and/or randomly arranged vegetal material (see Figures 5, 8, 12, 13, 15, 26)(C. Marian pers. comm.).

The settlement of *Șoimuș-La Avicola (Ferma 2)* developed between *ca.* the end of 6<sup>th</sup> and the beginning of the 5<sup>th</sup> millennium BC. There are good parallels in terms of relative chronology with other traditions, such as Vinča C, late Boian, Hamangia and Vădastra.

Good analogies for other impressed vessel bottoms are present in styles like Vădastra, eponymous settlement (Dragoman 2013, fig. 3.9/1, 2), Hamangia, at Baia-Golovița (Berciu 1966, 249, fig. 147/1, 2, 9-11) and Cheia-Vatra satului (V. Voinea pers. comm.), Boian, at Radovanu-*La Muscalu* (Comșa 1974, 91, fig. 24), Turdaș, eponymous settlement (von Roska 1941, 198, Pl. LXXVII/4-16) or Vinča, at Liubcova-*Ornița* (Luca 1998, 185, fig. 19/10). This type of archaeological find is present also in slightly later traditions like Stoicani-Aldeni, at Vulcănești (Dragomir 1983, fig. 41/4) and Stoicani (Petrescu-Dâmbovița 1953, 66, fig. 26/9, 10; 76, fig. 29/1) or Foeni, at Pianu de Jos-*Podei* (Bem 2015, fig. 110/5, 6).

We also observed that at least a part of the collection of vessel bottoms were not put on mat-like vegetal material, but simply on gathered vegetation (as in the case of Figures 12, 13, 15 and 26).



Figure 26. *Șoimuș-La Avicola (Ferma 2)*: impressed vessel bottom from Feature 482 (photo R. Petcu).

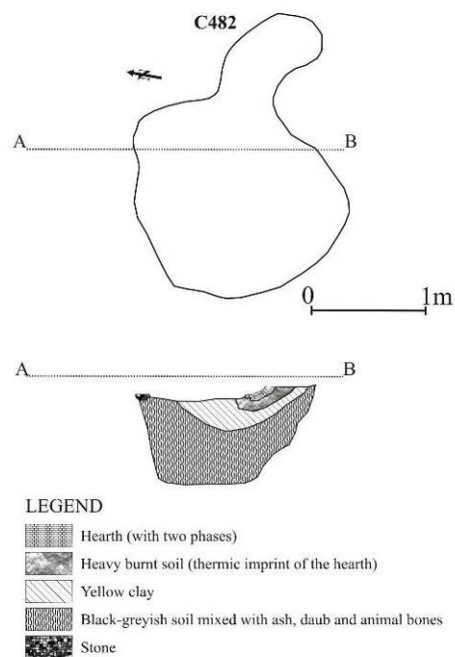


Figure 27. *Șoimuș-La Avicola (Ferma 2)*: Feature 482.

### A small scale experiment

We made an experiment with some grey club-rush gathered from a place near Bucharest (*Schoenoplectus lacustris* subsp. *tabernaemontani*). Grey club-rush is a perennial, aquatic plant from the class of Cyperaceae (Figure 28a); it is still used by local artisans. It has a weed-like aspect and grows as big tufts, rich in leaves. The leaves are linear and cylindrical with a green-greyish colour (Anghel *et al.* 1975, 353-354).

We plaited these leaves in order to make a little fragment of mat (Figure 28b). The next step was to create a vessel fragment from clay and then to imprint the mat on it (Figure 28c-f). This imprint on the soft fabric of the vessel bottom was compared with our Neolithic pot bottoms, in order to observe possible similarities (Figure 28g). Our clay imprint is very different compared with the vessel bottoms discovered at *Șoimuș*, in terms of the type of plant patterns. The plants used in the Neolithic settlement had wider, leaves, so it is probable that plants other than grey club-rush were used in the process of making pots. We suggest other plants with a wider body, perhaps bulrush (*Typha*) were used.

For the Cucuteni area a wide range of plants were used to make mat-like artifacts: different kind of reed, bulrush, sedge, raffia or cereals (Marian 2009, 57-58). Also, three types of impressions were documented on Cucutenian vessel bottoms: spiral, rosette-like and by a “weaving method” (Marian 2009, 58-71, figs. 35-49).



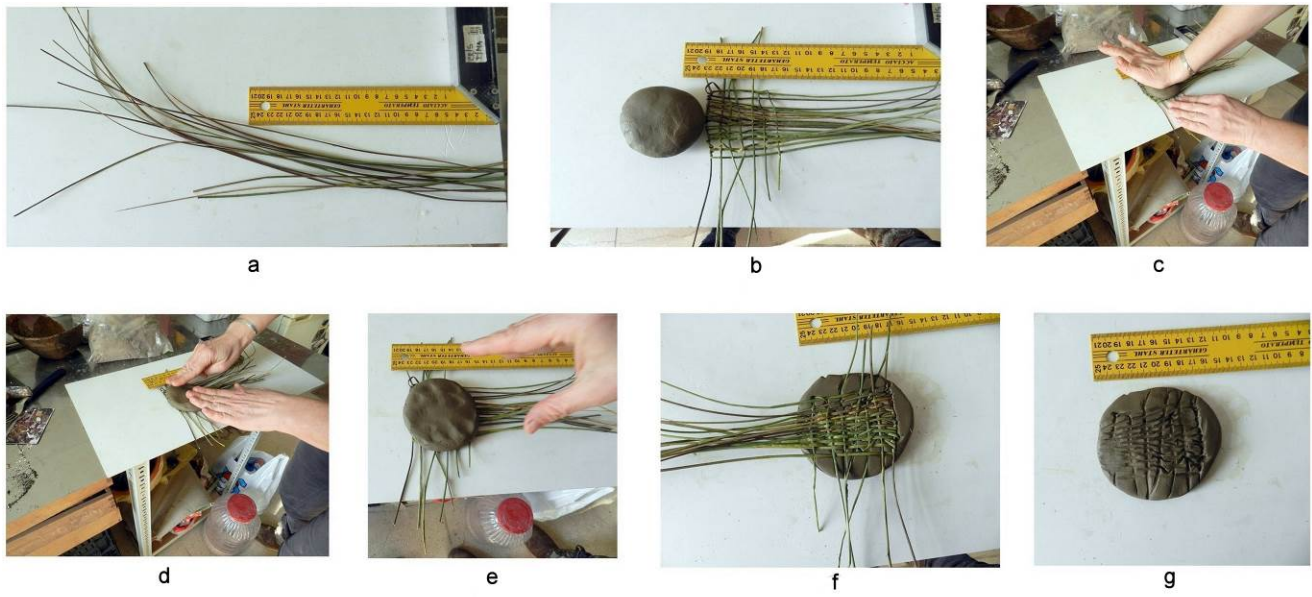


Figure 28. The stages of the experimental imprint (photo C.E. Ștefan).

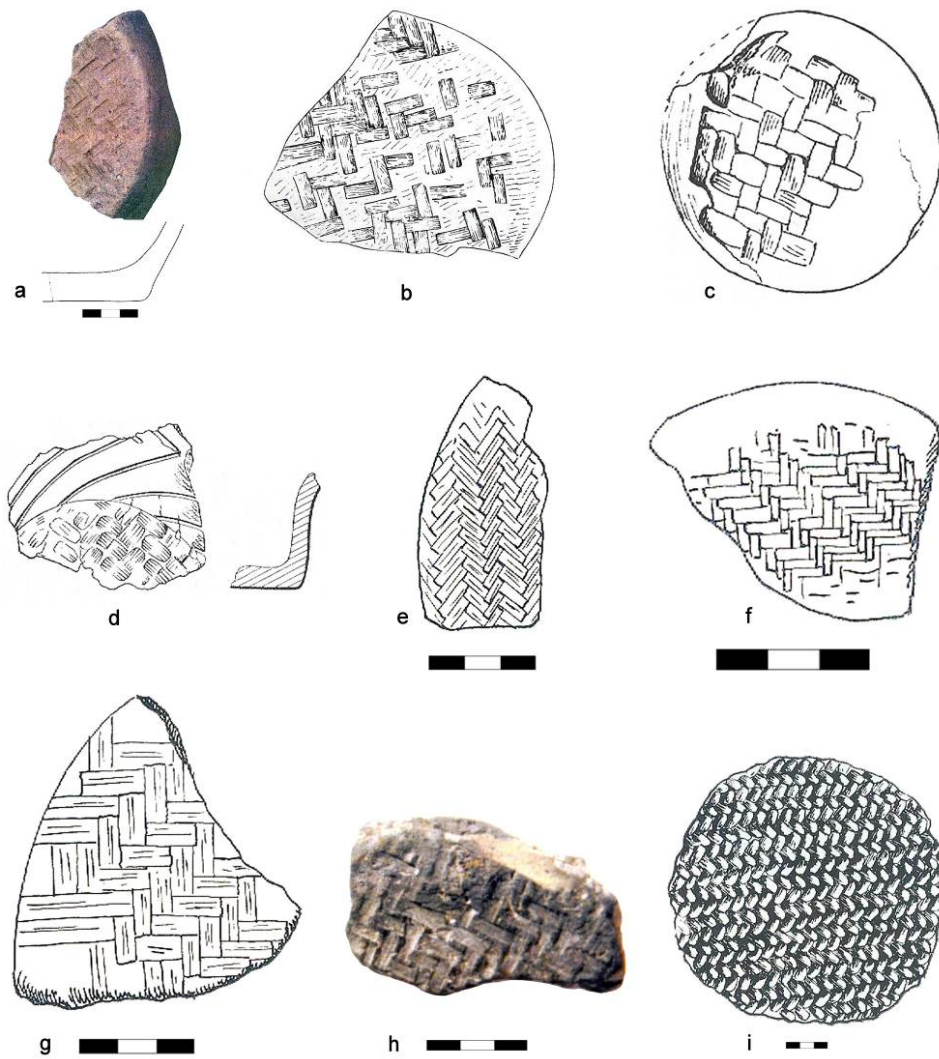


Figure 29. Prominent types of mats present in other Neolithic traditions of the Lower Danube. a: Pianu de jos; b: Radovanu; c-d: Stoicani; e-g: Turdaș; h: Vadastra; i: Vulcanesti.



If we look at our vessel bottoms from Şoimuş we can observe that most of them have a “woven” imprint on them. It appears to be the prominent type of mat present in all Neolithic traditions of the Lower Danube (Figure 29).

### Conclusions

Only a small number of the vessels recovered from Neolithic settlements bare evidence of vegetal imprints on their bases. The majority of the pottery had smooth bases. If the goal of placing the vessels on mats was for rapid detachment of the pottery from their support (during firing?) why were all the vessels not put on such mats? Could this be a special stage in pottery making specific only to certain potters?

In our opinion it is important in archaeology to understand the action of prehistoric people. We can access only a small part of their actions by studying some of the enduring materials like clay, stone, bone, etc. A large part of the Neolithic legacy is lost including wooden and vegetal artifacts, but also ideas, concepts, beliefs.

The interesting fact is that the spread of this practice of placing fresh modelled vessels on mat-like material over large geographical areas, from Hamangia in the east to Vinča and Turdaş in the west; this fact could be a result either of travelling potters, or of the spread of a practical idea. Most of the pot bottoms present a weave pattern which could suggest that they were put on a vegetal item similar to a mat. On the other hand, a few of them have a less complex pattern, which would suggest that were laid-down simply on gathered vegetation.

### Acknowledgements

Many thanks are given to Mrs Cristina Georgescu, restorer at “Vasile Pârvan” Institute of Archaeology, for the experimental part, support and advice and to Mrs Carmen Marian for her comments on the plant impressions.

### References

- Anghel, Gh., Nyárády, A., Păun, M. and Grigore, St. 1975. *Botanică*. Bucharest.
- Bem, C. 2015. *Sistemul de fortificare al stațiunii eneolitice de la Pianu de Jos Podei (Alba, România. Între simbolism și rațiuni defensive*. Bucharest.
- Berciu, D. 1966. *Cultura Hamangia*. Bucharest.
- Comşa, E. 1974. *Istoria comunităților culturii Boian*. Bucharest.
- Dobrescu, R., Ştefan, C. E. and Bonsall, C. Observations sur l'industrie en obsidienne découverte à Şoimuş-La Avicola (Ferma 2). *Materiale și Cercetări Arheologice (Serie Nouă)* XII, 45-56.
- Dragoman, R-A. 2013. *O biografie a ceramicii neolitice de la Vădastra*. Bucharest.
- Dragomir, I. T. 1983. *Eneoliticul din sud-estul României. Aspectul cultural Stoicani-Aldeni*. Bucharest.
- Luca, S. A. 1998. *Liubcova-Ornița. Monografie arheologică*. Târgoviște.
- Marian, C. 2009. *Meșesuguri textile în cultura Cucuteni*. Iași.
- Mărgărit, M., Ştefan, C.E. and Dumitraşcu, V. The exploitation of animal resources in Şoimuş-La Avicola (Ferma 2) settlement (Romania). *Documenta Praehistorica* XLIII, 363-397.
- Niță, L., Ştefan, C. E., Dimache, M., Hila, T. and Petcu, R. 2015. Considerații privind industria litică de la Şoimuş ‘La Avicola (Ferma 2)’, jud. Hunedoara. *Buletinul Muzeului Județean Teleorman* 7, 97-116.
- Petcu, R., Petcu, Răz. and Heroiu, A. 2012. Şoimuş 1 (Avicola), km. 29+750 – 30+300. *Cronica Cercetărilor Arheologice din România. Campania 2011*, 291-292. Bucharest.
- Petrescu-Dâmbovița, M. 1953. Cetățuia de la Stoicani, *Materiale și Cercetări Arheologice* I, 13-155.
- von Roska, M. 1941. *Die Sammlung Zsófia von Torma in der numismatisch-archaeologischen Abteilung der siebenbürgischen Nationalmuseums*. Kolozsvár.
- Ştefan, C. E., Petcu, R. and Petcu, Răz. 2013. Reprezentări antropomorfe din așezarea neolitică de la Şoimuş-La Avicola (Ferma 2), jud. Hunedoara. *Studii de Preistorie* 10, 49-66.
- Ştefan, C. E. 2014. Some special clay artifacts from Şoimuş-La Avicola (Ferma 2), Hunedoara County, Romania. *The Old Potter's Almanack* 19(2), 14-22.
- Ştefan, C. E. and Petcu, R. 2015. Notă asupra unor capace de lut cu trăsături umane de la Şoimuş-La


Avicola (Ferma 2), jud. Hunedoara. *Studii de Preistorie* 12, 117-126.

Ștefan, C. E., Petcu, R. and Petcu, Răz. 2015. Vase cu picioare de la Șoimuș-La Avicola (Ferma 2), jud. Hunedoara. *Studii și cercetări de istorie veche și arheologie* 66(3-4), 183-209.

Ștefan, C. E. 2016. Playing with clay: the anthropomorphic figurines from Șoimuș-La Avicola (Ferma 2), Hunedoara County, *DACIA N.S.* LX, 31-66.

Ștefan, C. E., Dimache, M., Petcu, Răz and Palcu, D. 2017. The polished stone industry from Șoimuș-La Avicola (Ferma 2), Hunedoara County, *Materiale și Cercetări Arheologice S.N.* XIII, 171-189.

## CONFERENCE DIARY

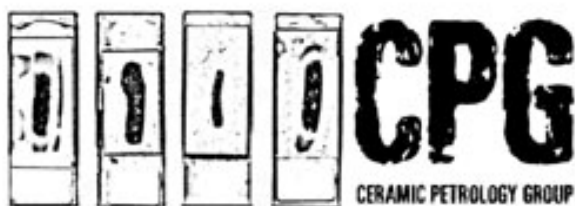

**Ceramic Petrology Group (CPG) Annual General Meeting**  
**8-9 November 2018, Competence Center**  
**Archaeometry - Baden-Wuerttemberg,**  
**University of Tübingen, Germany**

The 2018 CPG annual meeting will take place at the University of Tübingen (Germany). Papers are welcome on all aspects of archaeometric and experimental analysis of ceramics, plaster and other related materials.

For more information:

<https://uni-tuebingen.de/fakultaeten/mathematisch-naturwissenschaftliche-fakultaet/fachbereiche/geowissenschaften/arbeitsgruppen-kontakte/mineralogie-geodynamik/forschungsbereich/cca-bw/cpg-2018/>



**MetArh: Methodology and Archaeometry**  
**6-7 December 2018, University of Zagreb,**  
**Croatia**

This is the 6<sup>th</sup> appointment for the *Methodology and Archaeometry* conference, which is organised by the Department of Archaeology, Faculty of Humanities and Social Sciences of the University of Zagreb. The conference encourages interdisciplinarity, critical thinking, and new insights and approaches, as well as theoretical frameworks in contemporary archaeological science. Coverage of a wide spectrum of themes and scientific disciplines has resulted in papers and discussions that promote scientific issues in the fields of methodology, documentation and interpretation of archaeological data.

For more information:

<http://www.ffzg.unizg.hr/metarh/>



**ECerS XVI Ceramics in Cultural Heritage and Art**  
**16-20 June 2019, Politecnico di Torino, Italy**

The XVI<sup>th</sup> conference of the European Ceramic Society will take place at the Politecnico di Torino (Italy). It will host a one-day symposium dedicated to “Ceramics in Cultural Heritage and Art”.

The symposium will focus on ceramic and glass materials as cultural heritage objects, by addressing, although not limited to, the following subjects: characterisation of materials by invasive, non-invasive or micro-invasive methods, origin of raw materials, manufacturing technologies, decay mechanisms, conservation materials and methods. In addition, “immaterial aspects”, such as trading, authorship, heritage values, and social interactions of ceramics heritage will also be considered.

For more

information: <https://www.ecers2019.org/call-for-abstract/ceramics-in-cultural-heritage-and-art/>

---

## THE OLD POTTER'S ALMANACK

*The Old Potter's Almanack* is the joint letter of the Ceramic Petrology Group and the Prehistoric Ceramics Research Group. It is a venue for presenting current projects, research, reviews, information and topics of interest on all aspects of pottery, ceramics and refractory materials to the audience of scholars, experts, students, interested groups and individuals. The OPA is now published on-line with Heidelberg University and reaches a world-wide audience (see below for website link).

We welcome contributions focussing on any aspect of ceramics technology from any period, culture and geographic locality. Topics can cover materials from collections, museums, excavations and experimental work.

The deadline for copy of articles for the next issue of the OPA is 28<sup>th</sup> February 2019 (guidelines for contributors are available from the Editor). Copy and other information, news and events should be sent to the Editor, Michela Spataro (for details see below).

### Hon. Editor of the OPA

Michela Spataro

Dept. of Scientific Research  
The British Museum, London WC1B 3DG  
Email: [michelaspataro@yahoo.co.uk](mailto:michelaspataro@yahoo.co.uk)

### Ceramic Petrology Group (CPG) Hon. President

Ian Whitbread

School of Archaeology and Ancient History  
University of Leicester  
University Road, Leicester LE1 7RH  
Email: [ikw3@leicester.ac.uk](mailto:ikw3@leicester.ac.uk)

### Ceramic Petrology Group (CPG) Hon. Secretary

Patrick Quinn

UCL Institute of Archaeology  
31-34 Gordon Square, London WC1H 0PY  
Email: [patrick.quinn@ucl.ac.uk](mailto:patrick.quinn@ucl.ac.uk)

### Production Editor of the OPA

Nigel Meeks

Dept. of Scientific Research  
The British Museum, London WC1B 3DG  
Email: [nmeeks@britishmuseum.org](mailto:nmeeks@britishmuseum.org)

### Prehistoric Ceramics Research Group (PCRG) Secretary

Sarah Percival

NPS Archaeology, Scandic House  
85 Mountergate, Norwich NR1 1PY  
Email: [sarah.percival@nps.co.uk](mailto:sarah.percival@nps.co.uk)

### Prehistoric Ceramics Research Group Treasurer

Grace Jones

Bournemouth University, Fern Barrow, Poole,  
Dorset, BH12 5BB, United Kingdom  
Email: [gjones@bournemouth.ac.uk](mailto:gjones@bournemouth.ac.uk)

---

## WEBSITES

### The Old Potter's Almanack

<http://archiv.ub.uni-heidelberg.de/ojs/index.php/opa/index>

### Ceramic Petrology Group

<https://www.facebook.com/groups/TheCPG/>

### Prehistoric Ceramics Research Group

<http://www.pcr.org.uk/>

---